

# UNDER, OVER, AND IN THE MIX:

## A practical guide to telling the difference between types of polychrome decoration on English earthenware figures



Lauren Fair  
Winterthur Museum

### Introduction



The Thomas N. and A. Pat Bernard Collection of Staffordshire figures in the Ceramics and Glass Galleries at Winterthur

**Abstract** It is not always easy to identify the many different techniques used for decorating ceramics. After all, most materials are silicates pigmented with metallic oxides, with slight variations in composition, application method, and firing procedure. This poster aims to show the differences – both visual and chemical – among three decoration types: colored glazes, underglazes, and overglaze enamels.

**Staffordshire figures** are a unique group of earthenware figure sculpture and were popular collectible items in England and America during the 18<sup>th</sup> and 19<sup>th</sup> centuries. Taking after decorative traditions at porcelain factories such as Meissen and Sèvres, Staffordshire potteries created their own market by manufacturing luxury sculptures in

pale-bodied earthenware, making them affordable to the working class. Potters tried to achieve the best and brightest colors possible for their figures, during a time of much experimentation with color recipes.

**The Winterthur collection** of Staffordshire figures is the largest of its kind in an American museum, representing the full range of decoration techniques known to English potters at the time. This collection consists of approximately 270 figures, with dates ranging from 1740 to 1900, spanning the rise and fall of figure production in Staffordshire. Having such an extensive and representative group of objects in one location presented a unique opportunity for in-depth study and technical research.<sup>1</sup>

**Analysis** of the colorants of the different types of polychrome decoration on the Staffordshire figure collection informs the ceramic practices of the period and demonstrates differences between colored slips, underglaze oxides, colored glazes, underglaze Pratt colors, and overglaze enamels. Discussed here are the three most common types found on Staffordshire figures: colored glazes, Pratt colors, and enamels. A fourth form, a mystery blue glaze, is also presented, but warrants further research.



Purity, c. 1790-1810  
(2002.30.97)

### Colored glaze

Colored glazes are one of the earliest kinds of figure decoration, beginning in the second half of the 18<sup>th</sup> century and were made popular with the invention of liquid glaze and pearlware.

They consist of small amounts of metal oxides ground and dissolved in a lead glaze. They are applied to a bisque body by brush and are gloss-fired at 1050°C.

#### How can we tell? VISUAL


- Glossy surfaces
- Colors pooling in recesses of folds and drapery
- Areas of exposed bisque body where brush could not reach
- Limited colors possible




St. George and the dragon,  
c. 1780-1800 (2002.30.6)

#### How can we tell? CHEMICAL

- Ions are dissolved in glassy matrix
- Limited number of ions creates color:  
green (Cu<sup>2+</sup>), blue (Co<sup>2+</sup>),  
brown (Mn<sup>2+</sup>), yellow (Fe<sup>3+</sup>),  
purple (Mn<sup>3+</sup> and Co<sup>2+</sup>),  
black (Mn<sup>2+</sup>, Fe<sup>2+</sup> and Co<sup>2+</sup>)

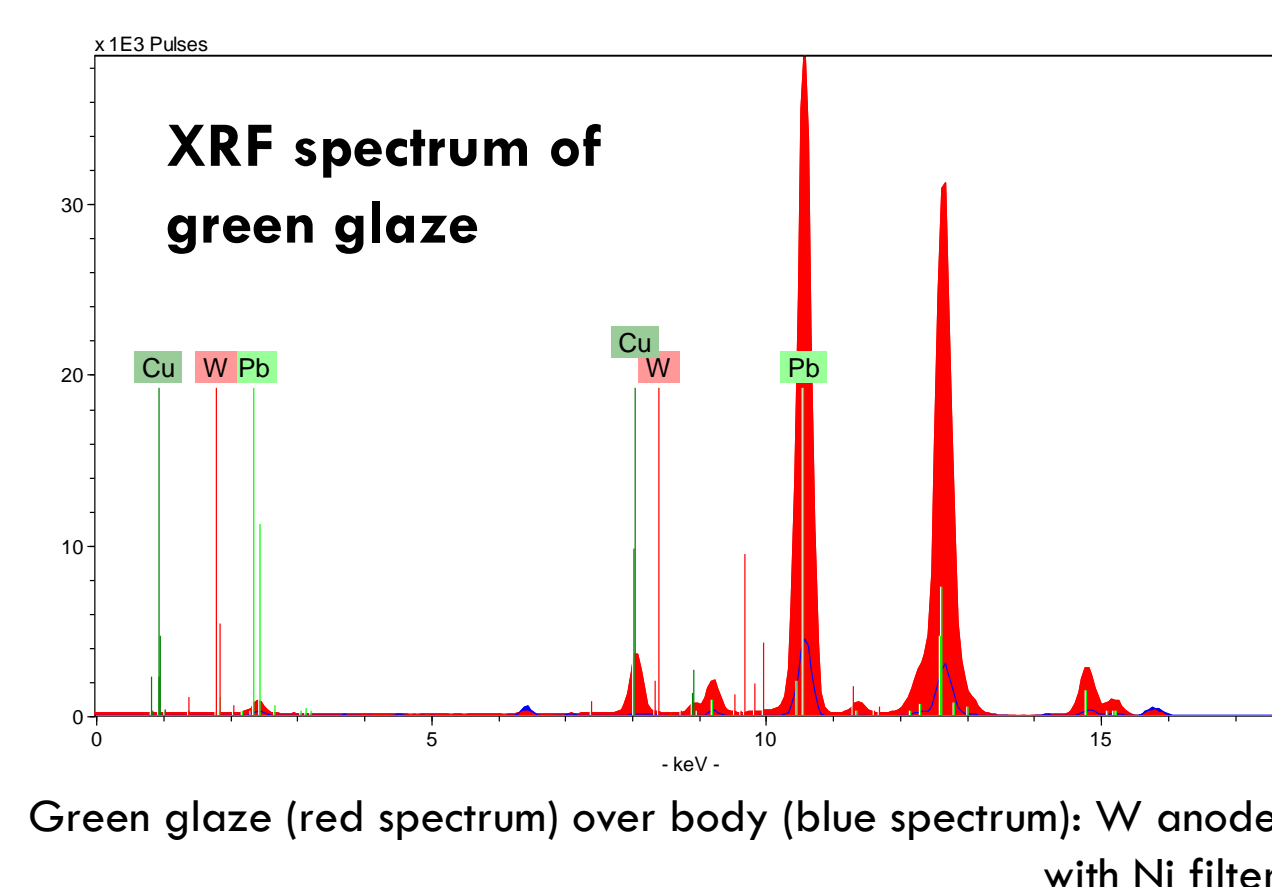

Green glaze (red spectrum) over body (blue spectrum) with Ni filter

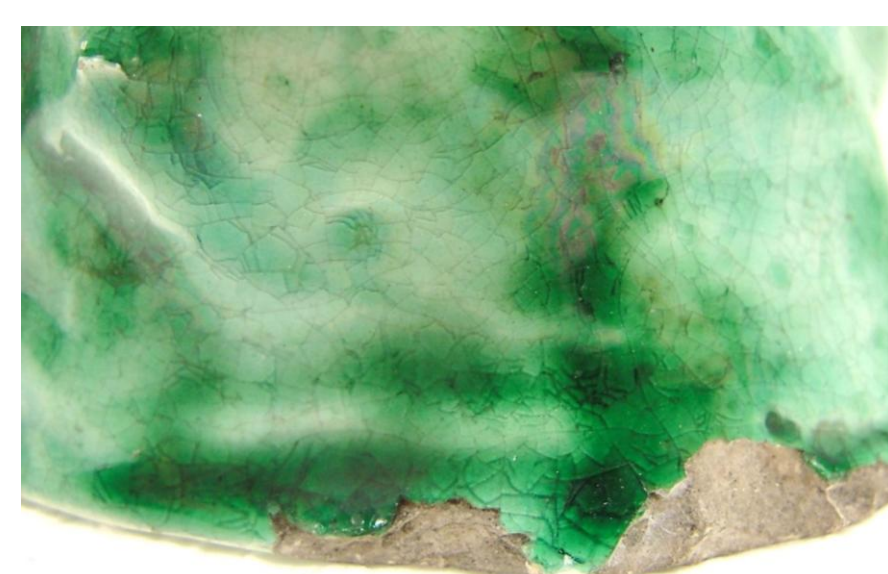

Green glaze

### Overglaze enamel

The development of enamels at the end of the 18<sup>th</sup> century allowed for an even greater color variety on figures. The range of colorants continued to expand throughout the 19<sup>th</sup> century. Many of the recipes followed Continental European technologies; but in some cases, Staffordshire enamels represent entirely new innovations.

Enamels are essentially low-fired colored glasses that consist of metal oxides ground with fluxes in a medium. They are applied to an already gloss-fired ceramic and then fired again in smaller kilns at successive firings between 700-900°C.

#### How can we tell? VISUAL


- Textures vary from matte to glossy
- Bubbling from firing is common
- Always occurs over the glaze
- More susceptible to surface abrasions, delamination, and flaking
- Great variety of colors including brilliant pinks, reds, turquoise, oranges, etc.



Shepherd and shepherdess,  
c. 1800-1820 (2002.30.57.1)

#### How can we tell? CHEMICAL

- Mixtures of metal oxides and lead or borax fluxes
- Pigments can be dissolved or dispersed  
e.g. orange enamels after ~1820 contain dispersed lead (II) chromate (PbCrO<sub>4</sub>) as the colorant

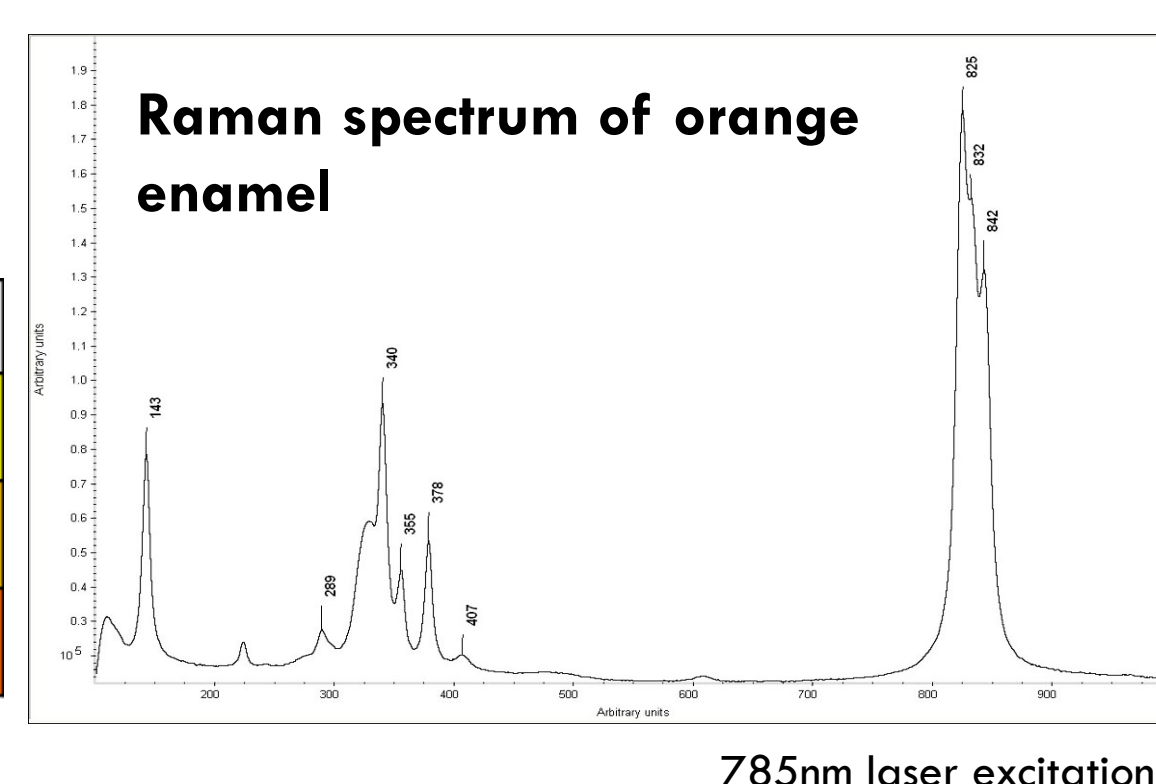

UCL Raman Library reference data 2011 with corresponding peaks to spectrum at right



orange and black enamels

Compound	Wavenumber (cm <sup>-1</sup> )
Chrome yellow (PbCrO <sub>4</sub> )	338w; 360s; 372m; 403w; 841vs
Chrome yellow deep (PbCrO <sub>4</sub> ·PbO)	336w; 358s; 374m; 401w; 838vs
Chrome yellow-orange (PbCrO <sub>4</sub> ·PbO)	149m; 346w(br); 828vs


### Underglaze (Pratt colors)

Underglaze Pratt colors were developed in Staffordshire in last decade of the 18<sup>th</sup> century to expand the decorating color palette beyond colored glazes and underglaze oxides already in use – the “new” colors consist of oxides able to withstand high gloss-firing temperatures.

They contain concentrated amounts of metal oxides ground with a medium, applied to a bisque body by brush, and dried completely. They are then dipped in lead glaze and fired at 1050°C.

#### How can we tell? VISUAL

- Glossy surfaces
- Mixtures of color particles often visible under the glaze
- Total glaze coverage from dipping
- Palette contains blue, olive greens and browns, muted oranges and yellows

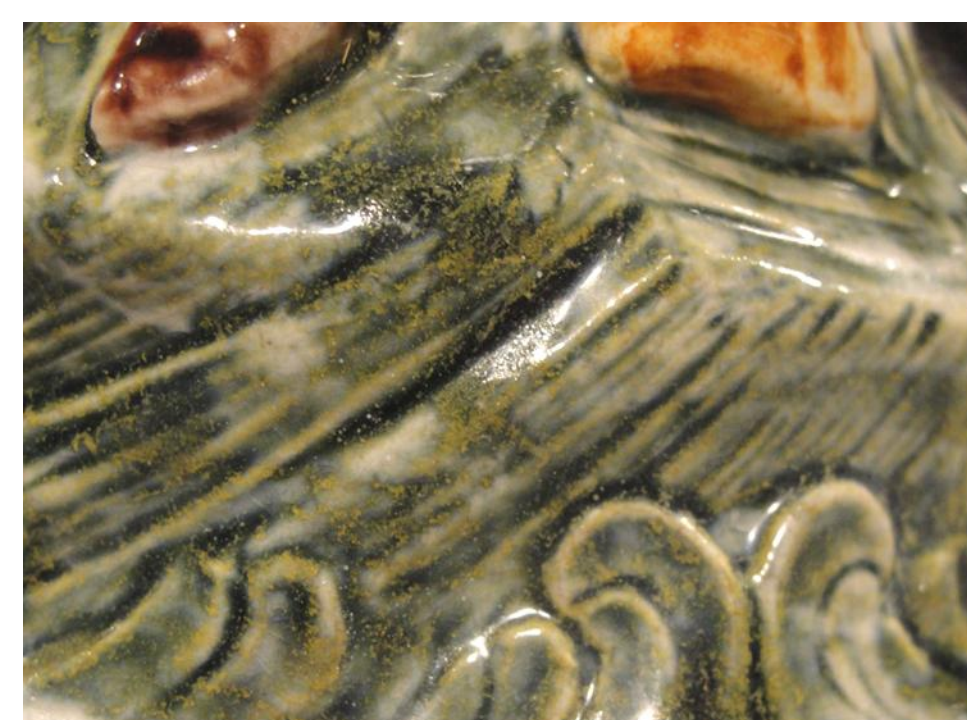


Green underglaze



Man with lost sheep,  
c. 1795-1810  
(2002.30.14)

#### How can we tell? CHEMICAL

- Mixtures of concentrated pigments create color
- Pigments are dispersed color compounds (not dissolved)  
e.g. green underglaze contains a mixture of cobalt blue (Co<sup>2+</sup>), Naples yellow (Pb<sub>2</sub>Sb<sub>2</sub>O<sub>7</sub>) and lead-tin yellow (Pb<sub>2</sub>SnO<sub>4</sub>)

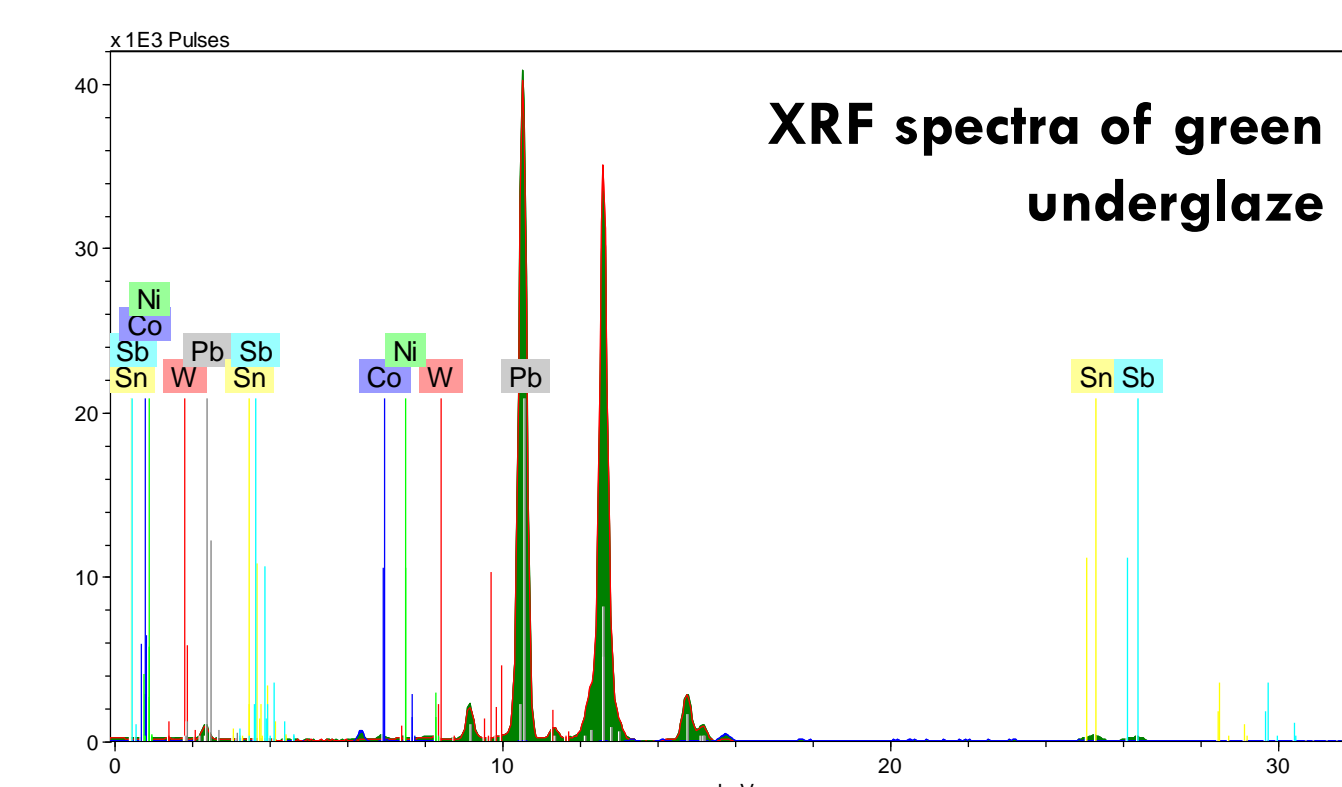

Green underglaze (green spectrum) over glaze (red spectrum) and body (blue spectrum): W anode with Ni filter




Olive brown glaze in cross-section  
100X with polarized light microscope, visible light

pigments undissolved in clear glaze  
earthenware body

XRF spectrum above and cross-section image at left demonstrate underglaze Pratt color technology as consisting of mixtures of concentrated pigments

SEM-EDS map of orange enamel in cross-section

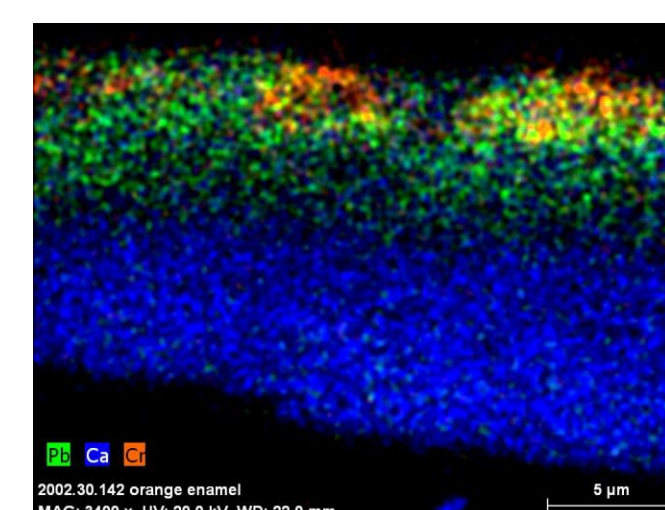

SEM-EDS map above shows cross-section with calcium-rich body, lead glaze, and lead/chromium-containing enamel layer


Raman spectrum at left shows mixture of lead chromates in 19<sup>th</sup>-c. orange enamels

### Mystery blue ?

A second type of blue overglaze decoration appears in the mid-19<sup>th</sup> century, primarily used to decorate the jackets on figures.



Will Watch,  
c. 1845-1860,  
(2002.30.123)

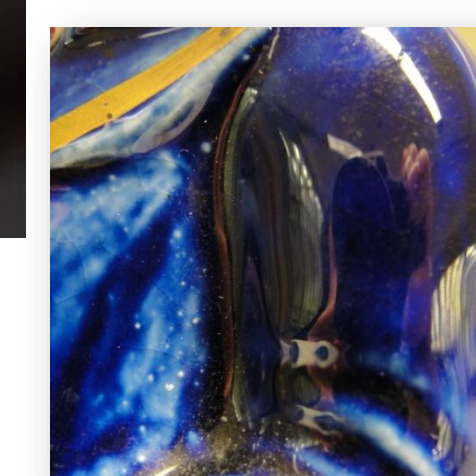

#### What do we think?

- Colorant is cobalt (Co<sup>2+</sup>)
- Glossy, rich blue color that appears to be in glaze matrix
- Possibly applied over top of glazed/fired surface and passed through small oven to let color sink into glaze layer, before applying other enamels.<sup>2</sup>

